

## boway 51100

### Material Designation

Boway Designation	boway 51100
UNS	C51100
EN	CuSn4
JIS	C5111
GB(China)	QSn4-0.3

### Chemical Composition\*

Sn	4	%
P	0.03-0.35	%
Cu	Rem.	


\* Nominal composition

### Application Target

Signal connector	Suitable
Power connector	Not recommended
Miniaturized connector	Suitable
Switch/Relay	Suitable
Semiconductor	Not recommended

### Fabrication Properties

Cold forming	Very good
Machining	Average
Electroplating	Very good
Hot dip tinning	Very good
Laser welding	Good
Resistance welding	Good
Soft soldering	Very good

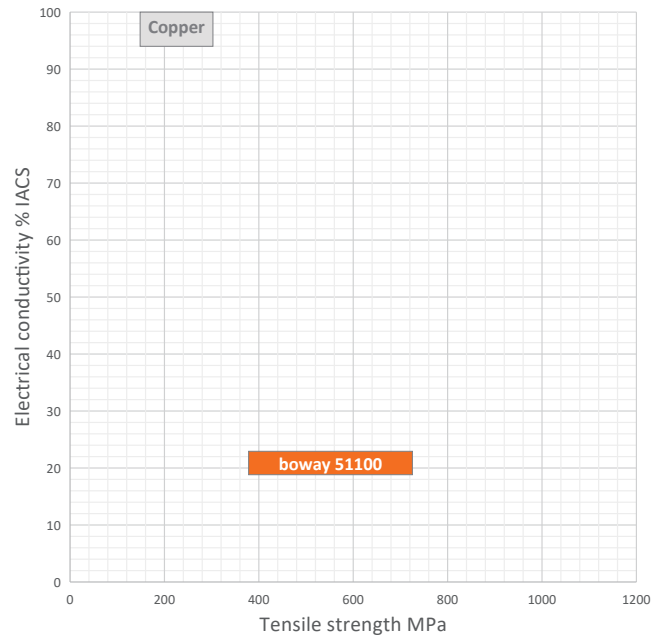

### Characteristics

Excellent formability and medium/high strength combined with low sensitivity to stress corrosion cracking.  
Very good corrosion resistance as well as excellent solderability.

### Physical Properties\*

Density	8.8	g/cm <sup>3</sup>
Electrical conductivity@20°C	19	% IACS
conductivity@20°C	11	MS/m
Thermal conductivity@20°C	100	W/(m·K)
Specific heat capacity	0.377	J/(g·K)
Modulus of elasticity	120	GPa
Poisson's ratio	0.33	
Coefficient of thermal expansion**	17.8	10 <sup>-6</sup> /K

\* Typical values at room temperature for reference

\*\* Average value between 20-300°C

# boway 51100

## Mechanical Properties (Values Underlined Are For Reference Only)

Temper	Tensile strength		Yield strength	Elongation	Hardness
	MPa	ksi	MPa	A50 %	HV
R380(1/2H)	380–485	55–70	≥ 290	≥ 12	<u>110–160</u>
R460(3/4H)	460–565	67–82	≥ 440	≥ 6	<u>150–190</u>
R495(H)	495–600	72–87	≥ 485	≥ 2	<u>160–200</u>
R580(EH)	580–685	84–99	≥ 560	≥ 1	<u>190–230</u>
R625(SH)	625–725	91–105	≥ 605	≥ 1	<u>200–240</u>
Annealed*	315–370	46–54	≥ 110	≥ 45	
H01*	315–400	46–58	≥ 140	≥ 25	
H02*	380–485	55–70	≥ 290	≥ 12	
H03*	460–565	67–82	≥ 440	≥ 6	
H04*	495–600	72–87	≥ 485	≥ 2	
H06*	580–685	84–99	≥ 560	≥ 1	
H08*	625–725	91–105	≥ 605	≥ 1	
H10*	660–750	96–109	≥ 635	≥ 1	

\*According to ASTM B888


## Bendability Bending thickness ≤ 0.5 mm; Bending width: 10 mm

Temper	90° R/T		180° R/T	
	Good Way	Bad Way	Good Way	Bad Way
R380	0	0	0	0
R460	0	0	0	1
R495	0	0.5	0	1.5
R580	0.5	1.5	1	2
R625	1.5	2.5	2	3.5

90° bend test according to EN ISO7438, 180° bend test according to ASTM B820, shown values might show orange-peel, however no crack.

## boway 51100

### Thermal Stress Relaxation

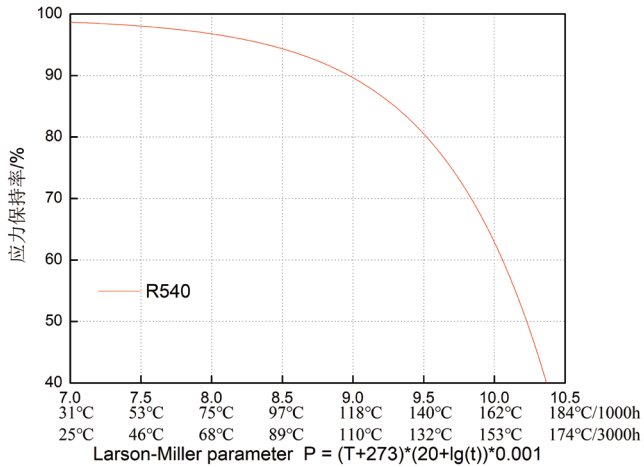

P=Larson Miller parameter

T=temperature( °C)

t=time(h)

Example: P=10 is equivalent to 162 °C/1000h


### Packaging

Standard coils with outside diameter up to 1300 mm.  
 Traverse-wound coils with drum weight up to 500 kg.  
 Multiple-coil up to 3 tons.

### Dimensions Available

Strip thickness 0.08–3.0 mm, other gauges on request.  
 Strip width from 8.5 mm.  
 Electroplated and Hot-dip tinned strip available.

### Electrical Conductivity

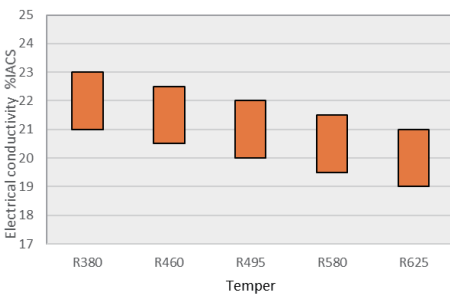

### Fatigue Strength

The fatigue strength is defined as the maximum bending stress amplitude which a material withstands for 10,000,000 load cycles under symmetrical alternate load without breaking. It depends on the temper selected and can be estimated typically by 1/3 of tensile strength.

This datasheet is for your general information only and is not subject to revision. No claim can be derived from it unless there is evidence of intent or gross negligence. The data given is to our best knowledge, no warranty can be derived from the data provided. The given info may not replace the customers own tests.